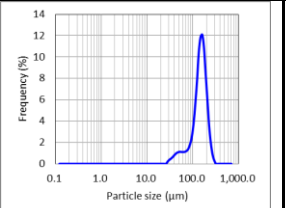
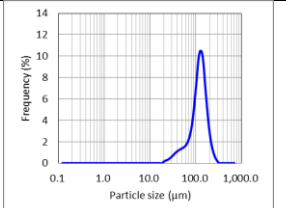
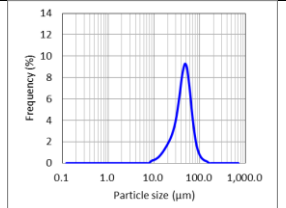
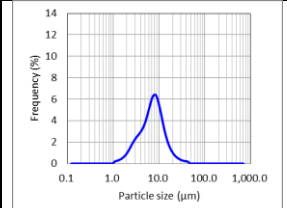
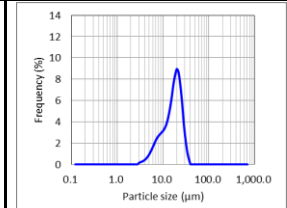
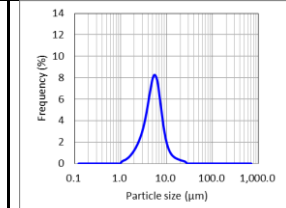
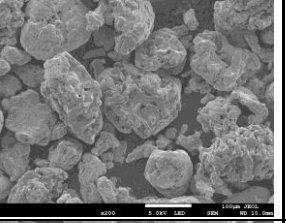
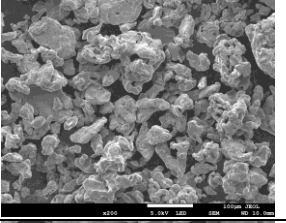
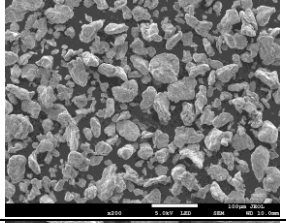
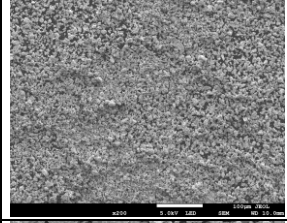
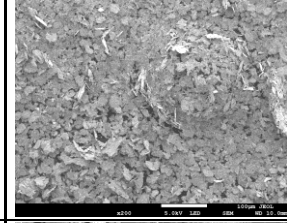
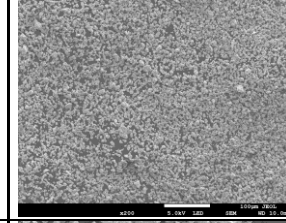
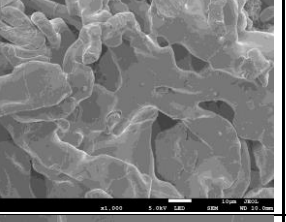
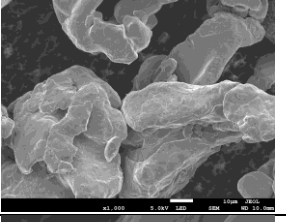
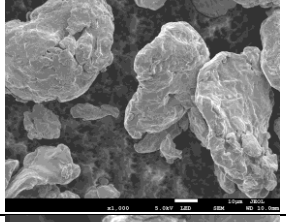
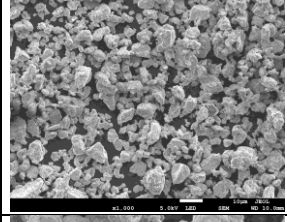
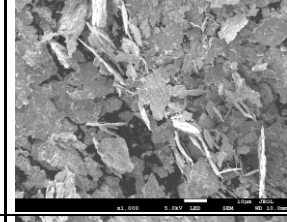
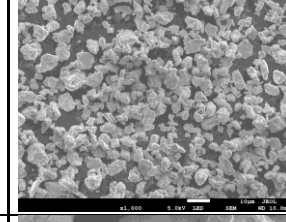


軟磁性粉用途向け 還元鉄粉 7 μ m~150 μ m

Particle size		150 μ m	100 μ m	40 μ m	7 μ m	7 μ m Flake	5 μ m
Type		High purity	High purity	High purity	High purity + Fine	High purity + Fine, Flake (Development products)	High purity + Fine (Development products)
Specific Surface Area		0.10 m ² /g	0.11 m ² /g	0.12 m ² /g	0.60 m ² /g	1.42 m ² /g	0.57 m ² /g
TAP Density		2.6 g/cm ³	2.9 g/cm ³	3.1 g/cm ³	3.6 g/cm ³	2.2 g/cm ³	3.5 g/cm ³
Oxygen		0.40 wt%	0.37 wt%	0.25 wt%	0.64 wt%	1.58 wt%	0.67 wt%
Particle Size Distribution	D10	72 μ m	54 μ m	21.3 μ m	2.8 μ m	7.0 μ m	2.5 μ m
	D50	142 μ m	116 μ m	42.8 μ m	7.0 μ m	16.5 μ m	5.0 μ m
	D90	199 μ m	173 μ m	67.4 μ m	14.0 μ m	25.3 μ m	8.7 μ m
	D95	217 μ m	195 μ m	77.4 μ m	17.8 μ m	27.9 μ m	10.9 μ m
Hc		5 Oe	6 Oe	7 Oe	18 Oe	27 Oe	17 Oe
σ_s		203 emu/g	202 emu/g	204 emu/g	202 emu/g	198 emu/g	201 emu/g
Particle Size Distribution chart							
SEM Image	×200						
	×1,000						
	×5,000	